

Two-orbital model explains the higher transition temperature of the single-layer Hg-cuprate superconductor compared to that of the La-cuprate superconductor

Hirofumi Sakakibara¹, Hidetomo Usui¹, Kazuhiko Kuroki^{1,4*}, Ryotaro Arita^{2,4,5}, and Hideo Aoki^{3,4}

¹*Department of Applied Physics and Chemistry, The University of Electro-Communications, Chofu, Tokyo 182-8585, Japan*

²*Department of Applied Physics, The University of Tokyo, Hongo, Tokyo 113-8656, Japan*

³*Department of Physics, The University of Tokyo, Hongo, Tokyo 113-0033, Japan*

⁴*JST, TRIP, Sanbancho, Chiyoda, Tokyo 102-0075, Japan and*

⁵*JST, CREST, Hongo, Tokyo 113-8656, Japan*

(Dated: August 4, 2010)

In order to explore the reason why the single-layered cuprates, $\text{La}_{2-x}(\text{Sr/Ba})_x\text{CuO}_4$ ($T_c \simeq 40\text{K}$) and $\text{HgBa}_2\text{CuO}_{4+\delta}$ ($T_c \simeq 90\text{K}$), have such a significant difference in T_c , we study a two-orbital model that incorporates the d_{z^2} orbital on top of the $d_{x^2-y^2}$ orbital. It is found, with the fluctuation exchange approximation, that the d_{z^2} orbital contribution to the Fermi surface, which is stronger in the La system, works against d -wave superconductivity, thereby dominating over the effect of the Fermi surface shape. The result resolves the long-standing contradiction between the theoretical results on Hubbard-type models and the experimental material dependence of T_c in the cuprates.

PACS numbers: 74.20.-z, 74.62.Bf, 74.72.-h

The physics of high- T_c superconductivity, despite its long history, harbors rich problems which are still open. Specifically, given the seminal discovery of the iron-based superconductors[2] and their striking material dependence of T_c [3], it should be important as well as intriguing to have a fresh look at the cuprates, which still have the highest T_c to date, to understand their material dependence of the T_c . One of the basic problems is the significant difference in T_c within the single-layered materials, i.e., $\text{La}_{2-x}(\text{Sr/Ba})_x\text{CuO}_4$ with a maximum T_c of about 40K versus $\text{HgBa}_2\text{CuO}_{4+\delta}$ with a $T_c \simeq 90\text{K}$. Phenomenologically, it has been recognized that the materials with $T_c \sim 100\text{K}$ tend to have “round” Fermi surfaces, while the Fermi surface of the La system is closer to a square shape which implies a relatively better nesting[4, 5].

Conventionally, the materials with a rounded Fermi surface have been modeled by a single-band model with large second ($t_2(>0)$) and third ($t_3(<0)$) neighbor hopping integrals, while the “low- T_c ” La system has been considered to have smaller t_2, t_3 . This, however, has brought about a contradiction between theories and experiments. Namely, while some phenomenological[6] and t - J model[7, 8] studies give a tendency consistent with the experiments, a number of many-body approaches for the Hubbard-type models with realistic values of on-site U show suppression of superconductivity for large $t_2 > 0$ and/or $t_3 < 0$, as we shall indeed confirm below[9].

To resolve this discrepancy, here we consider a two-orbital model that explicitly incorporates the d_{z^2} orbital on top of the $d_{x^2-y^2}$ orbital. The former component has in fact a significant contribution to the Fermi surface in the La system. We shall show that the key parameter that determines T_c is the energy level difference between the $d_{x^2-y^2}$ and d_{z^2} orbitals, i.e., the weaker the d_{z^2} contribution to the Fermi surface, the better for d -wave superconductivity, where a weaker contribution of the d_{z^2} results in a rounded Fermi surface (which in itself is not desirable for superconductivity), but it is the

“single-orbital nature” that favors a higher T_c dominating over the effect of the Fermi surface shape for the La system.

Let us start with a conventional calculation for the single-band Hubbard Hamiltonian, $H = \sum_{ij\sigma} t_{ij} c_{i\sigma}^\dagger c_{j\sigma} + U \sum_i n_{i\uparrow} n_{i\downarrow}$. Here we take the nearest-neighbor hopping $-t_1$ ($\simeq 0.4\text{eV}$, see table I) to be the unit of energy, $U = 6$, the temperature $T = 0.03$, and the band filling $n = 0.85$ are fixed, while we vary $t_2 = -t_3$ with $t_2 > 0$. We then apply the fluctuation exchange approximation (FLEX)[10, 11] to solve the linearized Eliashberg equation. T_c is the temperature at which the eigenvalue λ of the Eliashberg equation reaches unity, so λ at a fixed temperature can be used as a measure for the strength of the superconducting instability. We show in Fig.1 λ as a function of $(|t_2| + |t_3|)/|t_1| (= 2|t_2|/|t_1| \text{ here})$, which just confirm that, within the single-band model, λ (hence T_c) monotonically decreases with increasing $|t_2|$ and $|t_3|$. A calculation with the dynamical cluster approximation (DCA) shows that a negative t_2 works destructively against d -wave superconductivity[12], and a more realistic DCA calculation that considers the oxygen p_σ orbitals for the La and Hg cuprates also indicates a similar tendency[13]. As mentioned above, this seems to contradict with the experimental results that the materials with larger t_2 and t_3 have actually higher T_c ’s[4].

TABLE I: Hopping integrals within the $d_{x^2-y^2}$ orbital for the single and two orbital models, and $\Delta E \equiv E_{x^2-y^2} - E_{z^2}$.

	1-orbital		2-orbital	
	La	Hg	La	Hg
$t_1[\text{eV}]$	-0.444	-0.453	-0.471	-0.456
$t_2[\text{eV}]$	0.0284	0.0874	0.0932	0.0993
$t_3[\text{eV}]$	-0.0357	-0.0825	-0.0734	-0.0897
$(t_2 + t_3)/ t_1 $	0.14	0.37	0.35	0.41
$\Delta E[\text{eV}]$	-	-	0.91	2.19

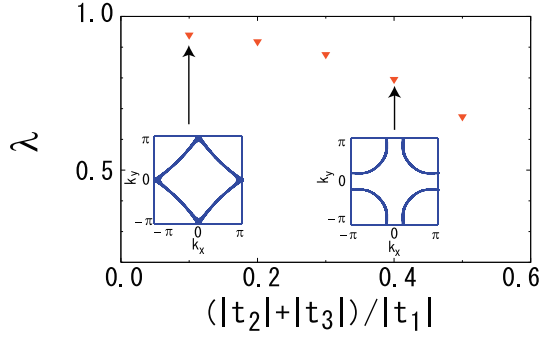


FIG. 1: FLEX result for the eigenvalue, λ , of the Eliashberg equation for the single-band Hubbard model plotted as a function of $(|t_2| + |t_3|)/|t_1|$, where we take $t_2 = -t_3 > 0$ for $U = 6|t_1|$, $T = 0.03|t_1|$, and the band filling $n = 0.85$. Fermi surfaces are displayed for two cases (indicated by arrows).

To resolve this, we now introduce the $d_{x^2-y^2}$ - d_{z^2} two-orbital model. For the La system, it has long been known that a band with a strong d_{z^2} character lies rather close to the Fermi energy[14–16]. More recently, it has been discussed in Refs.[4, 17] that the shape of the Fermi surface is determined by the energy level of the “axial state” consisting of a mixture of Cu d_{z^2} -O p_z and Cu $4s$ orbitals, and that the strength of the d_{z^2} contribution causes the difference in the Fermi surface shape between the La and Hg systems. Namely, the d_{z^2} contribution is large in the La system making the Fermi surface closer to a square, while the contribution is small in the Hg system making the Fermi surface more rounded. In Fig.2, we show the present, first-principles[18] result for band structures in the two-orbital model for the La and Hg systems, obtained by constructing maximally localized Wannier orbitals[19]. The lattice parameters adopted here are experimentally determined ones for the doped materials[20, 21]. We can here confirm that in the La system the main band (usually considered to be the “ $d_{x^2-y^2}$ band”) has in fact a strong d_{z^2} character on the Fermi surface near the N point, which corresponds to the wave vectors $(\pi, 0), (0, \pi)$ in the Brillouin zone of the square lattice. The d_{z^2} contribution is seen to “push up” the van Hove singularity (vHS) of the main band, resulting in a seemingly well nested (square shaped) Fermi surface. In the Hg system, on the other hand, the d_{z^2} band stays well away from E_F , and consequently the vHS is lowered, resulting in a rounded Fermi surface.

If we estimate in the two-orbital model the ratio $(|t_2| + |t_3|)/|t_1|$ within the $d_{x^2-y^2}$ orbitals, we get 0.35 for the La system against 0.41 for Hg (table I), which are rather close to each other. This sharply contrasts with the situation in which the model is constrained into a single band. There, the Wannier orbital has mainly $d_{x^2-y^2}$ character, but has “tails” with a d_{z^2} character especially for the La system. Then the ratio $(|t_2| + |t_3|)/|t_1|$ in the single-orbital model reduces to 0.14 for La against 0.37 for Hg (table I), which is just the conventional view mentioned in the introductory part. From this, we can

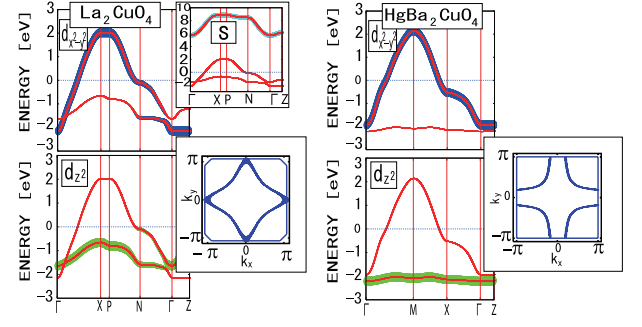


FIG. 2: The band structure in the two ($d_{x^2-y^2}$ - d_{z^2}) orbital model for La_2CuO_4 (left) and $\text{HgBa}_2\text{CuO}_4$ (right). The top (middle) panels depict the strength of the $d_{x^2-y^2}$ (d_{z^2}) characters with thickened lines, while the bottom panels the Fermi surfaces (for a total band filling $n = 2.85$). The inset shows the band structure of the three-orbital model (see text) for La system, where the $4s$ character is indicated.

confirm that it is the d_{z^2} contribution that makes the Fermi surface in the La system square shaped, while the “intrinsic” Fermi surface of the high T_c cuprate family is, as in the Hg system, rounded.

Now we come to the superconductivity in the two-orbital model. For the electron-electron interactions, it is widely accepted that the intraorbital U is $7 - 10t$ (with $t \sim 0.45\text{eV}$) for the cuprates, so we take $U = 3.0\text{eV}$. The Hund’s coupling J (= pair-hopping interaction J') is typically $\sim 0.1U$, so here we take $J = J' = 0.3\text{eV}$, which gives the interorbital $U' = U - 2J = 2.4\text{eV}$. The temperature is fixed at $k_B T = 0.01\text{eV}$. As for the band filling (number of electrons/site), we concentrate on the total $n = 2.85$, for which the main band has 0.85. Here we apply the multiorbital FLEX, as described e.g. in ref.[23], for the three-dimensional lattice taking $32 \times 32 \times 4$ k -point meshes and 1024 Matsubara frequencies. We first focus on the La system, and investigate how the d_{z^2} orbital affects superconductivity. Namely, while the on-site energy difference, $\Delta E \equiv E_{x^2-y^2} - E_{z^2}$, between the two orbitals is $\Delta E \simeq 0.9\text{eV}$ for La_2CuO_4 (table I), we vary the value to probe how the Eliashberg eigenvalue λ for d -wave superconductivity behaves. The result in Fig.3 shows that λ is small for the original value of ΔE , but rapidly increases with ΔE , until it saturates for sufficiently large ΔE . Hence the superconductivity turns out to be enhanced as the d_{z^2} band moves away from the main band. Note that this occurs despite the Fermi surface becoming more rounded with larger ΔE , namely, the effect of the orbital character (smaller d_{z^2} contribution) dominates over the Fermi surface shape effect. Conversely, the strong d_{z^2} orbital character in the Fermi surface around the $(\pi, 0), (0, \pi)$ works destructively against d -wave superconductivity. Physically, the reason for this may be explained as follows. First, although the La system has a better nested Fermi surface, we find that the strength of the antiferromagnetic spin fluctuations (the spin susceptibility obtained in FLEX) in La is only as

large as that for Hg. This is intuitively understandable, since the two electrons on nearest-neighbor sites are less constrained to have antiparallel spins in order to gain kinetic energy when two orbitals are active as in La. Secondly, d -wave pairing has a rough tendency for higher T_c in bands that are nearly half filled, whereas the d_{z^2} orbital here is nearly full filled.

We now focus on how the lattice structure affects ΔE and hence superconductivity. This is motivated by the fact that ΔE should be controlled by the ligand field, hence by the height, h_O , of the apical oxygen above the CuO_2 plane[15]. To single out this effect, let us examine the two-orbital model for which we increase h_O from its original value $2.41\text{\AA}$ with other lattice parameters fixed. In Fig.4(a), which plots the eigenvalue of the Eliashberg equation as a function of h_O , we can see that λ monotonically increases with the height. As seen from the inset of Fig.4(b), ΔE is positively correlated with h_O as expected, and Fig.4(b) confirms that the increase in λ is due to the increase in ΔE [24]. In these figures, we have also plotted the values corresponding to the Hg system obtained with the actual lattice structure. We can see that, while $h_O \simeq 2.8\text{\AA}$ for Hg is larger than $h_O \simeq 2.4\text{\AA}$ for La, $\Delta E \simeq 2.2\text{eV}$ for Hg is even larger than $\Delta E \simeq 1.3\text{eV}$, which is the value the La system would take for $h_O = 2.8\text{\AA}$. Consequently, λ for Hg is somewhat larger than that for the La system with the same value of h_O . This implies that there are some effects other than the apical oxygen height that also enhance ΔE in the Hg system, thereby further favoring d -wave superconductivity. In this context, the present result reminds us of the so-called ‘‘Maekawa’s plot’’, where a positive correlation between T_c and the level of the apical oxygen p_z hole was observed[25]. Since a higher p_z hole level (i.e., a lower p_z electron level) is likely to lower E_{z^2} , the positive correlation between ΔE and T_c found here is indeed consistent with Maekawa’s plot. It can be considered that in La cuprates, a considerable portion of the doped holes go

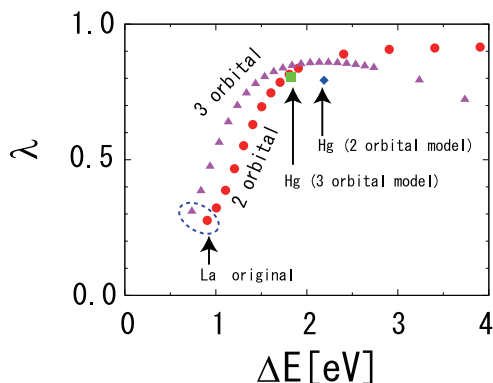


FIG. 3: The eigenvalue, λ , of the Eliashberg equation for d -wave superconductivity is plotted against $\Delta E = E_{x^2-y^2} - E_{z^2}$ for the two-orbital (red circles) or three-orbital (purple triangles) models for La_2CuO_4 . Corresponding eigenvalues for $\text{HgBa}_2\text{CuO}_4$ are also indicated.

into the apical oxygen p_z , and this effect is effectively taken into account in our model. A more detailed study on these issues is now under way, and will be discussed in a separate publication.

Finally, let us discuss the effect of Cu $4s$ orbital, which is the main component of the ‘‘axial state’’ discussed in Refs.[4, 17]. In the present two-orbital model the $4s$ orbital is effectively incorporated in both of the $d_{x^2-y^2}$ and d_{z^2} orbitals, i.e., the Wannier orbitals have tails that have the $4s$ character. In order to make the examination more direct, we now consider a three-orbital model that explicitly considers the $4s$ orbital. The band dispersion for the La system shown in the inset of Fig.2 shows that the $4s$ band lies well ($\simeq 7\text{ eV}$) above the Fermi level. Nonetheless, the $4s$ orbital gives an important contribution to the Fermi surface in that the ratio $(|t_2| + |t_3|)/|t_1|$ within the $d_{x^2-y^2}$ sector in the three-orbital model takes a much smaller value of 0.10, which should imply that it is the path $d_{x^2-y^2} \rightarrow 4s \rightarrow d_{x^2-y^2}$ that gives the effectively large t_2, t_3 , and hence the round Fermi surface, as pointed out previously[4, 17]. In this context, it is worth mentioning that the path $d_{x^2-y^2} \rightarrow d_{z^2} \rightarrow d_{x^2-y^2}$ also contributes to t_2, t_3 , but has an opposite sign to the $4s$ contribution because the d_{z^2} level lies below $d_{x^2-y^2}$, while $4s$ above $d_{x^2-y^2}$ [26]. So the two contributions to the main band cancel with each other, where the cancellation should be strong when the energy of the d_{z^2} orbital is high as in La.

We now apply FLEX to the three-orbital model varying $\Delta E = E_{x^2-y^2} - E_{z^2}$ as in the two-orbital model, where we fix the on-site energy difference $E_{4s} - E_{z^2}$ at its original value. We have chosen this because a similar three-orbital model constructed for Hg (not shown) shows that the on-site energy difference between the $4s$ and $d_{x^2-y^2}$ orbitals is smaller than in the La system by about 1eV , so in the Hg system, both of $E_{x^2-y^2} - E_{z^2}$ and $E_{4s} - E_{x^2-y^2}$ are smaller by about 1eV , which means that the d_{z^2} and $4s$ levels shift roughly in parallel relative to $d_{x^2-y^2}$. It can be seen in Fig.3 that the ΔE dependence of λ in the three-orbital model resembles that of the two-orbital model in the realistic ΔE range. (When ΔE becomes unrealistically large, i.e., when $4s$ level is

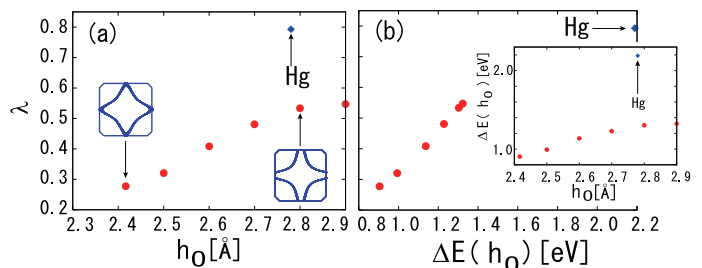


FIG. 4: The eigenvalue of the Eliashberg equation λ (red circles) when h_O (a) or ΔE (b) is varied hypothetically in the lattice structure of La_2CuO_4 . Blue diamond indicates the eigenvalue of $\text{HgBa}_2\text{CuO}_4$. Inset in (b) shows the relation between h_O and ΔE .

too close to the Fermi level, the Fermi surface becomes too deformed for superconductivity to be retained.) We have also calculated the eigenvalue for the Hg system in the three-orbital model, and obtained a value very similar to that obtained in the two-orbital model, as plotted in Fig.3. If we summarize the three-orbital results, while the 4s orbital has an important effect on the shape of the Fermi surface, this can be effectively included in the $d_{x^2-y^2}$ and d_{z^2} Wannier orbitals in the two-orbital model as far as the FLEX studies are concerned. This contrasts with the case of the d_{z^2} orbital, which, if effectively included in the $d_{x^2-y^2}$ Wannier orbital to construct a single-orbital model, would result in a different result. This conclusion is natural, since the energy difference ($\simeq 1$ eV) between $d_{x^2-y^2}$ and d_{z^2} orbitals in the La system is smaller than the electron-electron interaction, which is why the d_{z^2} orbital has to be explicitly considered in a many-body analysis, while the energy difference ($\simeq 7$ eV) between $d_{x^2-y^2}$ and 4s orbitals is much larger than the electron-electron interaction, so that the 4s orbital can effectively be integrated out before the many-body analysis. So the message here is that the two-orbital ($d_{x^2-y^2}$ - d_{z^2}) model suffices to discuss the material dependence of the T_c in the cuprates. Whether the effect of the d_{z^2} orbital can be further incorporated in the on-site U or off-site V values (i.e., material-dependent interaction values) in an effective, single-band model is a future problem.

To summarize, we have introduced a two-orbital model to understand the material dependence of T_c in the

cuprates. We have shown that the key parameter is the energy difference between the $d_{x^2-y^2}$ and d_{z^2} orbitals, where the smaller the contribution of the d_{z^2} orbital, the better for d -wave superconductivity, with the orbital-character effect superseding the effect of the Fermi surface shape. It is intriguing to note that the two high T_c families, cuprates and iron pnictides, exhibit material dependence of T_c that, according to the present study and Ref.[27], owes to the material dependent multiorbital band structures.

In the present view, the Hg cuprate is “ideal” in that the d_{z^2} band lies far below the Fermi level. Nevertheless, there is still room for improvement: as mentioned in the outset, within single-orbital systems higher T_c can be obtained for smaller t_2 and t_3 . It may be difficult to make t_2 and t_3 smaller in the cuprates, since they are intrinsically large as far as the Cu 4s orbital is effective. Conversely, we can predict that materials with an isolated single band that has smaller t_2 and t_3 should accommodate even higher T_c than the Hg cuprate, provided that the electron interaction is similar to those in the cuprates.

We wish to acknowledge Y. Nohara for the assistance in the band calculation of the Hg system. R.A. acknowledges X. Yang and O.K. Andersen for fruitful discussions. The numerical calculations were performed at the Supercomputer Center, ISSP, University of Tokyo. This study has been supported by Grants-in-Aid for Scientific Research from MEXT of Japan and from JSPS. H.U. acknowledges support from JSPS.

-
- [*] corresponding author: kuroki@vivace.e-one.uec.ac.jp
- [2] Y. Kamihara *et al.*, J. Am. Chem. Soc. **130**, 3296 (2008).
- [3] C.-H. Lee *et al.*, J. Phys. Soc. Jpn. **77**, 083704 (2008).
- [4] E. Pavarini *et al.*, Phys. Rev. Lett. **87**, 047003 (2001).
- [5] K. Tanaka *et al.*, Phys. Rev. B **70**, 092503 (2004).
- [6] T. Moriya and K. Ueda, J. Phys. Soc. Jpn. **63**, 1871 (1994).
- [7] C.T. Shih *et al.*, Phys. Rev. Lett. **92**, 227002 (2004).
- [8] P. Prelovšek and A. Ramšak, Phys. Rev. B **72**, 012510 (2005).
- [9] For a review, see D.J. Scalapino, *Handbook of High Temperature Superconductivity*, Chapter 13, Eds. J.R. Schrieffer and J.S. Brooks (Springer, New York, 2007).
- [10] N.E. Bickers *et al.*, Phys. Rev. Lett. **62**, 961 (1989).
- [11] T. Dahm and L. Tewordt, Phys. Rev. Lett. **74**, 793 (1995).
- [12] Th. Maier *et al.*, Phys. Rev. Lett. **85**, 1524 (2000).
- [13] P.R.C. Kent *et al.*, Phys. Rev. B **78**, 035132 (2008).
- [14] K. Shiraishi *et al.*, Solid State Commun. **66**, 629 (1988).
- [15] H. Kamimura and M. Eto, J. Phys. Soc. Jpn. **59**, 3053 (1990); M. Eto and H. Kamimura, J. Phys. Soc. Jpn. **60**, 2311 (1991).
- [16] A.J. Freeman and J. Yu, Physica B **150**, 50 (1988).
- [17] O.K. Andersen *et al.*, J. Phys. Chem. Solids **56**, 1573 (1995).
- [18] S. Baroni *et al.*, <http://www.pwscf.org/>. Here we take the exchange correlation functional introduced by J. P. Perdew *et al.* [Phys. Rev. B **54**, 16533 (1996)], and the wave functions are expanded by plane waves up to a cut-off energy of 60 Ry with 20^3 k -point meshes.
- [19] N. Marzari and D. Vanderbilt, Phys. Rev. B **56**, 12847 (1997); I. Souza, N. Marzari and D. Vanderbilt, Phys. Rev. B **65**, 035109 (2001). The Wannier functions are generated by the code developed by A. A. Mostofi *et al.*, (<http://www.wannier.org/>).
- [20] J.D. Jorgensen *et al.*, Phys. Rev. Lett. **58**, 1024 (1987).
- [21] J.L. Wagner *et al.*, Physica C **210**, 447 (1993).
- [22] The conclusion of the present study is not sensitive to the choice of the interaction values. For instance, if we raise the interactions to $U = 4.5\text{eV}$ ($\sim 10t$) and $J = 0.45\text{eV}$, the eigenvalue of the Eliashberg equation for the two-orbital model discussed in Fig.3 is only slightly modified to $\lambda = 0.29$ for La and 0.72 for Hg.
- [23] K. Yada and H. Kontani, J. Phys. Soc. Jpn. **74**, 2161 (2005).
- [24] Note that, while ΔE is varied “by hand” in the Hamiltonian in Fig.3, ΔE in Fig.4 is made to vary with h_O of the hypothetical lattice structure.
- [25] Y. Ohta, T. Tohyama, and S. Maekawa, Phys. Rev. B **43**, 2968 (1991).
- [26] When the d_{z^2} level rises above the $d_{x^2-y^2}$, it can play a role similar to 4s as shown in P. Hansmann *et al.*, Phys. Rev. Lett. **103**, 016401 (2009).
- [27] K. Kuroki *et al.*, Phys. Rev. B **79**, 224511 (2009).